arXiv:1604.07688v2 [cond-mat.stat-mech] 27 Oct 2016

Supplementary Information : Continuously Varying Critical Exponents Beyond Weak Universality

N. Khan[1], P. Sarkar[2], A. Midya[1] , P. Mandal[1] and P. K. Mohanty[1,*]
[1] *CMP Division, Saha Institute of Nuclear Physics, 1/AF Bidhan Nagar, Kolkata 700064, India*
[2] *Department of Physics, Serampore College, Serampore 712201, India*
[*] *Correspondence and requests for materials should be addressed to P.K.M. (email: pk@saha.ac.in)*

In this supplement, we provide additional details of the experiments and the scaling theory. We added two supplementary figures that describe the measurement of critical exponents on $(Sm_{1-y}Nd_y)_{0.52}Sr_{0.48}MnO_3$ single crystals with $y = 0.6, 0.8$ and 1. Also we provide an alternative scaling transformation of critical exponents.

Supplementary figures

The supplementary Fig. 1 describes determination of the critical point and exponents, and the scaling collapse for Nd doping $y = 1$- within error limits they are same as the critical exponents of Heisenberg Model in three dimension. Figure 2 describes the same, but for different doping $y = 0.6$ and 0.8.

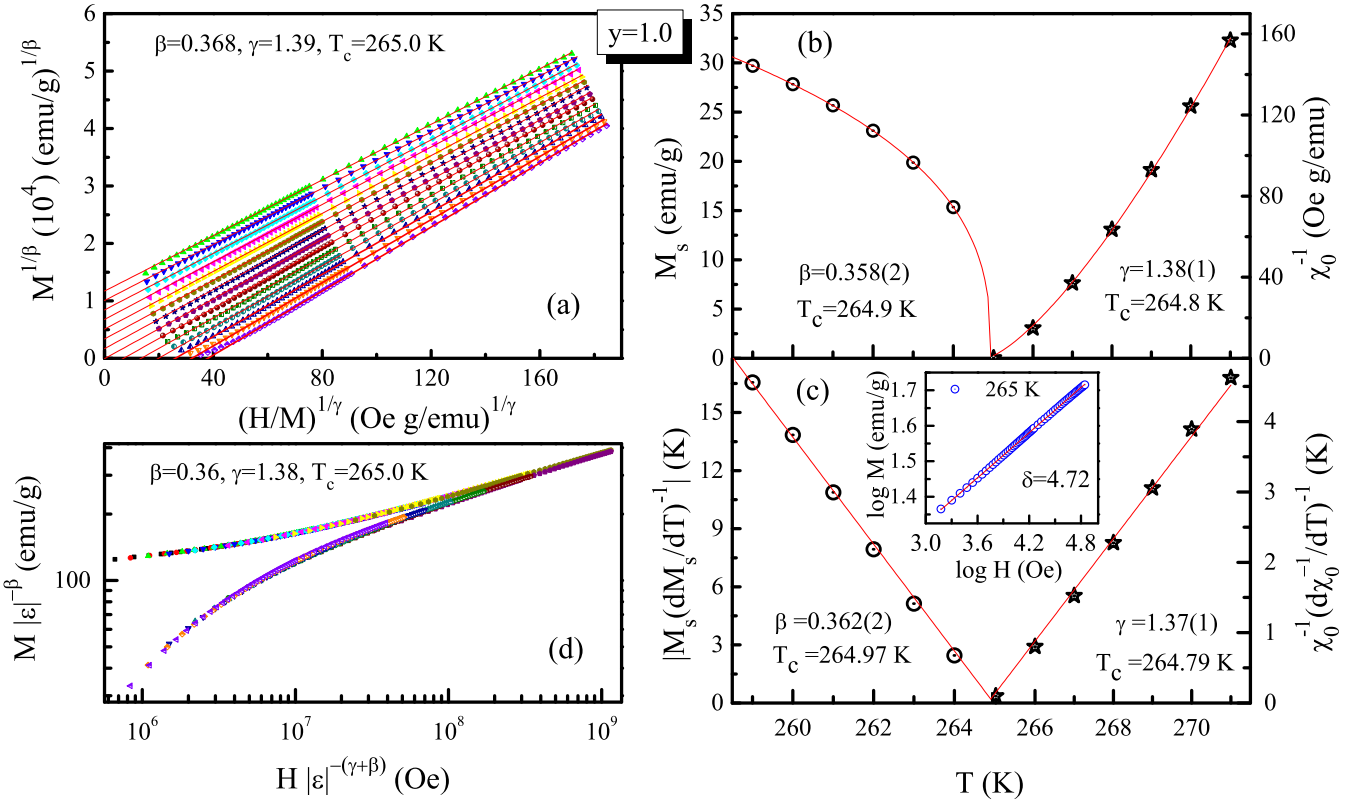

FIG. 1: (a) Modified Arrott plot [$M^{1/\beta}$ vs $(H/M)^{1/\gamma}$] isotherms (258 K $\leq T \leq$ 271 K in 1 K interval) of $(Sm_{1-y}Nd_y)_{0.52}Sr_{0.48}MnO_3$ (y=1) single crystal. Solid lines are the high-field linear fit to the isotherms. The isotherm at 265.0 K almost passes through the origin in this plot. (b) Temperature dependence of spontaneous magnetization, M_S (circle) and inverse initial susceptibility, χ^{-1} (star). Solid lines are the best-fit curves. (c) Kouvel-Fisher plots of M_S and ${\chi_0}^{-1}$. Inset shows log-log plot of M(H) isotherm at $T = T_C$ (d) Scaling collapse of $M - H$ curves: $M|\epsilon|^{-\beta}$ is an universal function of $H|\epsilon|^{-(\beta+\gamma)}$, indicating two universal curves below and above T_C.

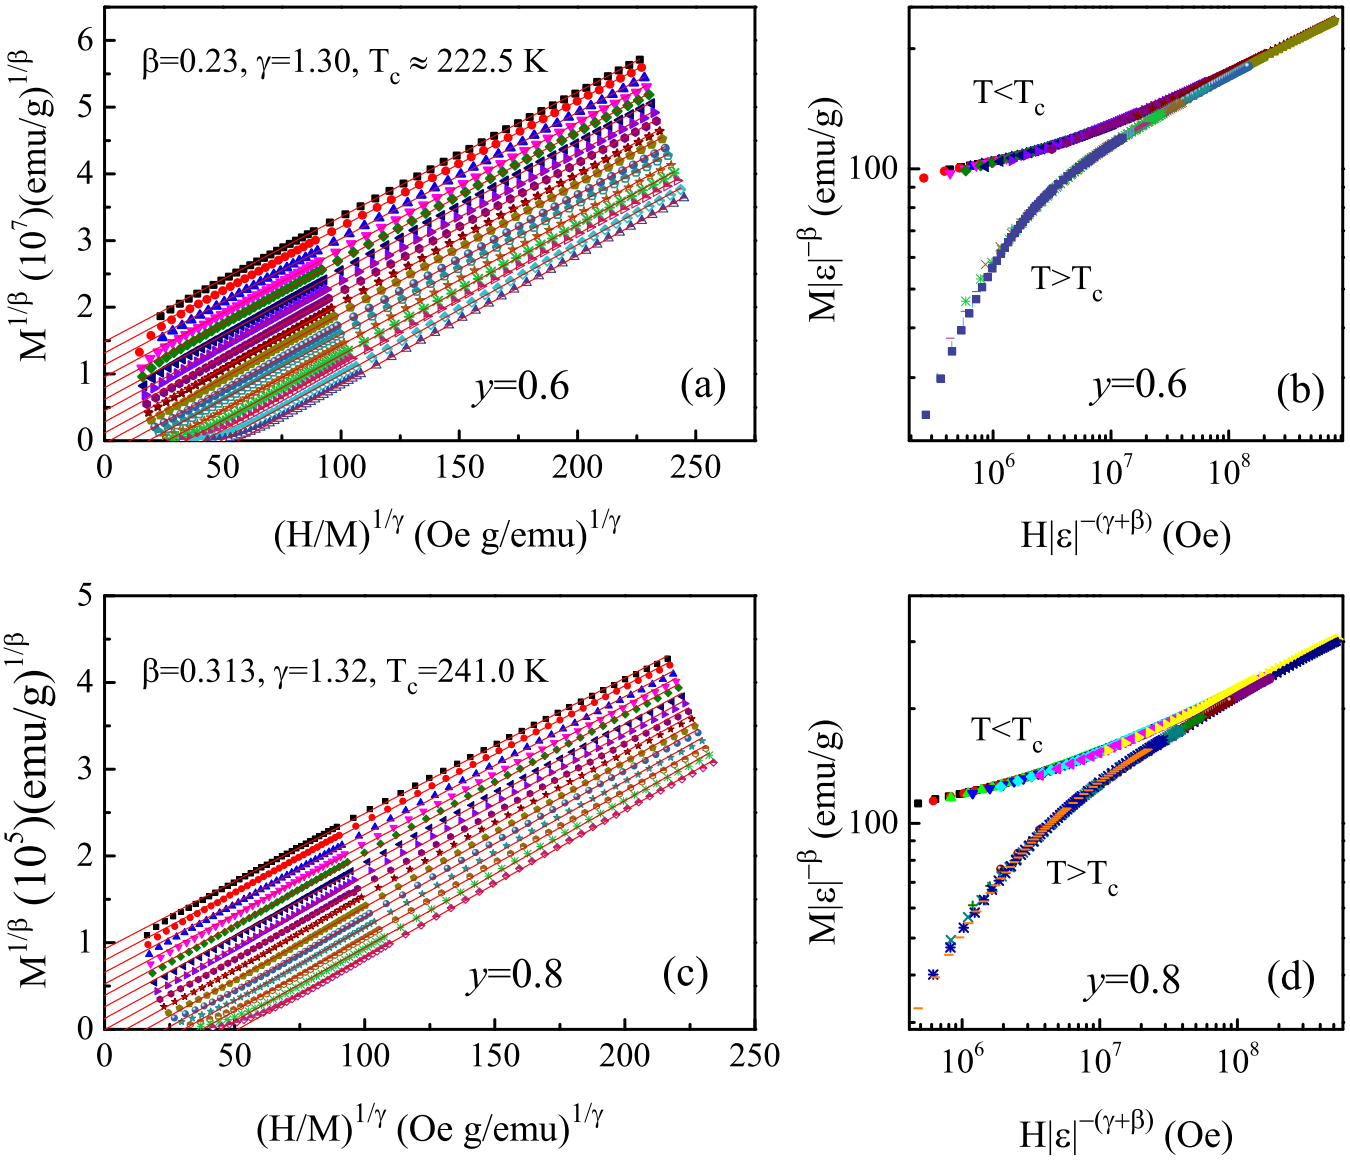

FIG. 2: (a) Modified Arrott plot [$M^{1/\beta}$ vs $(H/M)^{1/\gamma}$] for (a) $y = 0.6$ and (c) 0.8. The critical isotherm, which almost passes through the origin gives an estimate of respective $T_C \simeq 222.5$ K and 241 K. (b) and (d) : A plot of $M|\epsilon|^{-\beta}$ against $H\epsilon|^{-(\beta+\gamma)}$ show scaling collapse for $y = 0.6, 0.8$ respectively.

An alternative scaling

In the main text we have chosen the exponents γ and δ to scale independently

$$\gamma \to \frac{\gamma}{\lambda^{\omega}}; \frac{\delta+1}{\delta-1} \to \frac{1}{\lambda^{\kappa}} \frac{\delta+1}{\delta-1}. \tag{1}$$

But, since magnetic phase transitions are associated with *two* independent critical exponents, one can vary any two independently and fix variation of others through scaling relations. In theoretical studies, η and ν are natural choices as they can be obtained from the two-point correlation function,

$$\langle S(\vec{R})S(\vec{R}+\vec{r})\rangle - \langle S(\vec{R})\rangle^2 = \frac{e^{-|\vec{r}|/\xi}}{|\vec{r}|^{d-2+\eta}}, \tag{2}$$

where the correlation length $\xi \sim (T_c - T)^{-\nu}$. Also, η satisfy another hyper scaling relation,

$$2 - \eta = d\frac{\delta - 1}{\delta + 1} = \frac{\gamma}{\nu}. \tag{3}$$

Thus the variation we propose in the main text (Eq. (5)), is equivalent to

$$2 - \eta = \lambda^{\kappa}(2 - \eta_0) \ ; \ \nu = \frac{\nu_0}{\lambda^{\kappa+\omega}}. \tag{4}$$

Other exponents can be derived as they are functions of (η, ν),

$$\gamma = \nu(2 - \eta) \ ; \ \alpha = 2 - d\nu \ ; \ \beta = \frac{\nu}{2}(d - 2 + \eta) \ ; \ \delta = \frac{d + 2 - \eta}{d - 2 + \eta}$$

when scaling relations hold.

arXiv:1604.07688v2 [cond-mat.stat-mech] 27 Oct 2016

Continuously Varying Critical Exponents Beyond Weak Universality

N. Khan[1], P. Sarkar[2], A. Midya[1] , P. Mandal[1] and P. K. Mohanty[1*]
[1] *CMP Division, Saha Institute of Nuclear Physics, 1/AF Bidhan Nagar, Kolkata 700064, India*
[2] *Department of Physics, Serampore College, Serampore 712201 India*

Renormalization group theory does not restrict the from of continuous variation of critical exponents which occurs in presence of a marginal operator. However, the continuous variation of critical exponents, observed in different contexts, usually follows a weak universality scenario where some of the exponents (e.g., β, γ, ν) vary keeping others (e.g., δ, η) fixed. Here we report a ferromagnetic phase transition in $(\mathbf{Sm}_{1-y}\mathbf{Nd}_y)_{0.52}\mathbf{Sr}_{0.48}\mathbf{MnO}_3$ $(0.5 \leq y \leq 1)$ single crystal where *all* critical exponents vary with y. Such variation clearly violates both universality and weak universality hypothesis. We propose a new scaling theory that explains the present experimental results, reduces to the weak universality as a special case, and provides a generic route leading to continuous variation of critical exponents and multicriticality.

Study of critical phenomena is based on two concepts: one is universality [1, 2] which states that the associated critical exponents and scaling functions are universal up to symmetries and space dimensionality, and another is scaling theory [3] that describes the general properties of the scaling functions and relates different critical exponents. In the renormalization group approach [4], the critical point is a fixed point governed by a unique set of relevant operators with scaling dimensions (critical exponents) which are fully independent of irrelevant operators. While a relevant perturbation may take the system to a new fixed point, the marginal one brings in a possibility of a line of critical points having continuous variation of exponents. Although the concept of universality has been verified experimentally time and again, starting from early 40s [5] to present [6], a continuous variation is rarely observed. A clear example is provided by Baxter [7] who solved the eight vertex model [8] (EVM) exactly, and Kadanoff and Wegner [9] who provided a mapping of EVM to a two-layer Ising system with a marginal four-body interaction between the layers [10] (similar to Ashkin Teller model [11–13]) that drives the continuous variation. In later years, Suzuki [14] proposed a *weak* universality (WU) scenario where critical exponents (like β, γ, ν in EVM) may change continuously but their ratios ($\frac{\beta}{\nu}, \frac{\gamma}{\nu}$ and consequently $\delta = 1 + \frac{\gamma}{\beta}$) remain invariant. This WU scenario has been observed in frustrated spin systems [15, 16], interacting dimers [17], magnetic hard squares [18], Blume-Capel models [19], reaction diffusion systems [20], absorbing phase transitions [21], percolation models [22, 23], fractal structures [24], quantum critical points [25], etc. The generic nature of the marginal interaction that leads to weak universality in all these different systems remain unclear.

To the best of our knowledge, most systems which show continuous variation of critical exponents obey weak universality - a few exceptions include criticality in Ising spin glass [26], micellar solutions [27, 28], frustrated spin systems [29], strong coupling QED [30] etc. Unconventional exponents are also experimentally observed in several systems like weak ferromagnet $BaIrO_3$ ($\beta \approx 0.82, \gamma \approx 1.03$ and $\delta \approx 2.20$), organic ferromagnet TDAE-C_{60} ($\beta \approx 0.75$, $\gamma \approx 1.22$ and $\delta \approx 2.28$), quasi-two-dimensional organic conductor κ-(BEDT-TTF)$_2$Cu[N(CN)$_2$]Cl ($\beta \approx 1$, $\gamma \approx 1$ and $\delta \approx 2$), etc [31–33]. Recently, Fuch et. al. [34] have observed the linear variation of exponents in the polycrystalline samples of $Sr_{1-z}Ca_zRuO_3$ from $\{\beta \approx 0.5, \gamma \approx 1, \delta \approx 3\}$ for $z = 0$ to $\{\beta \approx 1, \gamma \approx 0.9$ and $\delta \approx 1.6\}$ for z=0.6, which satisfy Widom scaling relation ($\beta + \gamma = \beta\delta$) for all z. Authors have suggested that the evolution of exponents may be originating from orthorhombic distortions or additional quantum fluctuations associated with quantum phase transition.

Anomalous ferromagnetic (FM) transition has also been observed in mixed valance manganites, $RE_{1-x}AE_x\mathrm{MnO}_3$ (*RE*: rare earth ions, *AE*: alkaline earth ions) either as a discontinuous transition or a continuous transition with a set of critical exponents that does not belong to any known universality or the weak universality [35–46]. The unusual magneto-electronic properties in narrow band manganites are closely associated with the quenched disorder arising mainly due to the size mismatch between *A*-site cations [47, 48]. Such disorder reduces the carrier mobility and the formation energy for lattice polarons [49], in effect T_C reduces, rendering the FM transition towards first-order. A system with narrow bandwidth and large disorder such as $Sm_{1-x}Sr_x\mathrm{MnO}_3$ shows a sharp first-order FM transition for $x = 0.45 - 0.48$ [39–42]. The first-order transition is however extremely sensitive to external pressure, magnetic field, *A*-/*B*-site substitution, oxygen isotope exchange, etc. - with the application of external and internal pressure (chemical substitution) beyond a critical threshold, the transition becomes continuous [40–42, 50].

In this paper, we report two important results - a first-time observation of a thermodynamic transition (*i.e.* FM phase transition in $(\mathrm{Sm}_{1-y}\mathrm{Nd}_y)_{0.52}\mathrm{Sr}_{0.48}\mathrm{MnO}_3$) where *all* critical exponents vary continuously, and a new scaling theory that unifies the earlier observations of contin-

uous variation of exponents along with the present experimental results. We propose that, to obey the scaling relations consistently, the variation of critical exponents are constrained to have specific forms. This scaling hypothesis naturally leads to two special cases which have been realized earlier, namely the weak universality [14] (where δ is fixed) and the strong coupling QED [30] (fixed γ). A more generic scenario is the one which allows simultaneous variation of *all* the critical exponents in an intrigue way, leading to a multi-critical point where the phase transition becomes discontinuous. This scenario is verified experimentally in a comprehensive and systematic study of FM phase transition in $(Sm_{1-y}Nd_y)_{0.52}Sr_{0.48}MnO_3$ single crystal. For higher doping concentration $y > 0.4$, the FM transition is found to be continuous, but to our surprise, the critical exponents exhibit continuous variation with Nd concentration y, starting from $(\beta, \gamma, \delta) = (0.16, 1.27, 9.30)$ at $y = 0.5$ to $(0.36, 1.38, 4.72)$ at $y = 1$. Within error limits, $y = 1$ belongs to the universality class of Heisenberg model in three dimension (HM3d). The proposed scaling hypothesis successfully explains the continuous variation of exponents and predicts a discontinuous transition for $y < 0.37$ which has been observed recently by others [40, 41].

EXPERIMENTAL METHODS

The single crystals of $(Sm_{1-y}Nd_y)_{0.52}Sr_{0.48}MnO_3$ with $y = 0.5, 0.6, 0.8$ and 1.0 were prepared by floating zone technique under oxygen atmosphere [58, 59]. Single crystallinity was confirmed by the Laue diffraction. The dc magnetization measurements were performed using a Quantum Design magnetic property measurement system (MPMS SQUID VSM) in fields up to 7 T. The data were collected after stabilizing the temperature for about 30 min. External magnetic field was applied along the longest sample direction and data were corrected for the demagnetization effect.

RESULTS AND DISCUSSION

Critical temperature and exponents :

Let us set notations by reminding that in absence of magnetic field (H) the spontaneous magnetization of the system vanishes as $M_S(0, \varepsilon) \sim (-\varepsilon)^{\beta}$ and the initial susceptibility diverges as $\chi_0(0, \varepsilon) \sim (\varepsilon)^{-\gamma}$ as the critical point is approached, *i.e.,* when $(T/T_C - 1) \equiv \varepsilon \to 0$. Again at $T = T_C$, the magnetization varies algebraically $M(H, T_C) \sim H^{1/\delta}$ [51]. To estimate the critical exponents β, γ and δ, we need to know T_C accurately. To do so, we exploit the linearity in Arrott-Noaks equation of state [52]

$$\left(\frac{H}{M}\right)^{1/\gamma} = a\varepsilon + bM^{1/\beta}, \qquad (1)$$

where a, b are non-universal constants. The correct choice of β and γ can make the isotherms of $M^{1/\beta}$ versus $(H/M)^{1/\gamma}$ a set of parallel straight lines with *one* unique critical isotherm that passes through the origin. This is explained in Fig. 1(a) for $y = 0.5$ and the self consistency is achieved for the values $\beta = 0.16$, $\gamma = 1.30$. The isotherm $T = 192$ K passes almost through the origin.

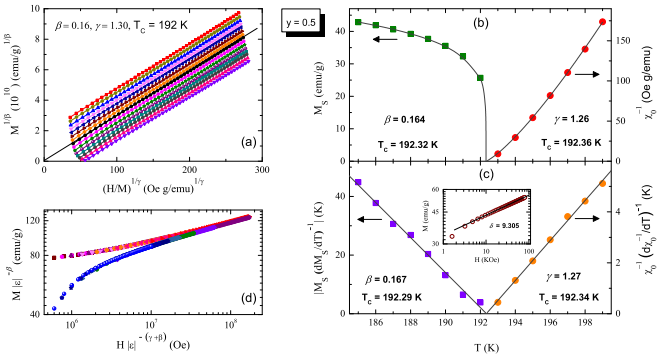

FIG. 1: (a) Modified Arrott plot [$M^{1/\beta}$ vs $(H/M)^{1/\gamma}$] isotherms (185 K$\leq$ T $\leq$199 K in 1 K interval) of $(Sm_{1-y}Nd_y)_{0.52}Sr_{0.48}MnO_3$ (y=0.5) single crystal. Solid lines are the high-field linear fit to the isotherms. The isotherm (at $T = 192$ K) closest to the Curie temperature ($T_C = 192.3$ K) almost passes through the origin in this plot. (b) Temperature dependence of spontaneous magnetization, M_S (square) and inverse initial susceptibility, χ_0^{-1} (circle). Solid lines are the best-fit curves. (c) Kouvel-Fisher plots of M_S and ${\chi_0}^{-1}$. Inset shows log scale plot of M(H) isotherm at $T = T_C$ (d) Scaling collapse of $M - H$ curves following Eq. (2), indicating two universal curves below and above T_C.

The Arrotts plots can be used further to get better estimates of β, γ and T_C. From the intercepts of these parallel lines on $M^{1/\beta}$ and $(H/M)^{1/\gamma}$ axes, we obtain M_S and χ_0^{-1} for different temperature which are shown in Fig. 1 (b). The best power-law fit gives rise to $\beta = 0.164 \pm 0.002$ with $T_C = 192.32 \pm 0.04$ K and $\gamma = 1.260 \pm 0.003$ with $T_C = 192.36 \pm 0.03$ K, respectively. As a final estimate, we take $T_C = 192.3$ K, $\beta = 0.16$ and $\gamma = 1.26$. These estimates are in fact consistent with Kouvel-Fisher criteria [53] which predict that in the scaling regime, both $M_S \left(\frac{dM_S}{dT}\right)^{-1}$ and $\chi_0^{-1} \left(\frac{d\chi_0^{-1}}{dT}\right)^{-1}$ are proportional to T with proportionality constants β^{-1} and γ^{-1} respectively; which is shown in Fig. 1(c). To estimate another critical exponent δ, we take the help of M-H isotherm at $T \simeq T_C$ (here $T = 192$K). The log-scale plot of M vs. H, as shown in the inset of Fig. 1(c), is linear with slope $\delta = 9.30$. Following the same method, we have determined the critical exponents and T_Cs' for $y = 0.6, 0.8$ and 1.0 [54] which are listed in Table I along with the

critical exponents of HM3d. The variation of T_C with y can be explained in terms of bandwidth and the local disorder [48] of the system. With increasing y, the bandwidth increases whereas disorder decreases; both these effects enhance T_C. It is clear from Table I that the exponents for $y = 1$ are same as that of HM3d within error limits whereas they deviate substantially and vary systematically when y is decreased. Clearly, β decreases whereas δ increases by *two*-fold as one goes from $y = 1$ to $y = 0.5$. On the other hand, for each $y = 0.5, 0.6, 0.8, 1$, the Widom scaling relation $\beta + \gamma = \beta\delta$ is satisfied. This indicates that the change in γ is minimal, as observed here. The variation of critical exponents with respect to a system parameter contradicts universality, moreover it violates WU as δ varies along with β and γ. The focus of current work is to address this issue in details, but first let us ask whether the scaling hypothesis, crucial for the description of near critical systems, is valid here.

y	T_C (K)	β	γ	δ
0.5	192.3	0.16	1.27	9.30
0.6	222.5	0.23	1.30	6.31
0.8	241.3	0.31	1.32	5.14
1.0	265.3	0.36	1.38	4.72
HM3d	-	0.365	1.386	4.82

TABLE I: Critical exponents of $(Sm_{1-y}Nd_y)_{0.52}Sr_{0.48}MnO_3$

For a thermodynamic system near FM transition, magnetization M depends on H and ε and follows a universal scaling form [51]

$$M(H, \varepsilon) = |\varepsilon|^{\beta} \mathcal{F}_{\pm}(H/|\varepsilon|^{\beta+\gamma}), \tag{2}$$

where $\mathcal{F}_+$ is for $T > T_C$ and $\mathcal{F}_-$ is for $T < T_C$. The utility of universal scaling function lies in the fact that the M-H curves obtained for different T (near T_C) can be collapsed on to a single curve when one plots $M/|\varepsilon|^{\beta}$ versus $H/|\varepsilon|^{\beta+\gamma}$. This scaling collapse is shown in Fig. 1(d) for $y = 0.5$ (and in [54] for other values of y); the two branches in this curve correspond to supper- and sub-critical phases. For $y = 0.6, 0.8$ and 1.0, the data collapse is also shown in Fig. 2(a), where we use an alternative but equivalent form of Eq. (2),

$$M(H, \varepsilon)^{-1/\beta} = \varepsilon \mathcal{F}(\varepsilon H^{-1/(\beta+\gamma)}). \tag{3}$$

It is advantageous to use this form as the two branches of Eq. (2) are now merged to a single function $\mathcal{F}$ with its argument $x = \varepsilon H^{-1/(\beta+\gamma)}$ extending from the sub-critical ($x < 0$) to the supper-critical ($x > 0$) regimes. A very good data collapse and - which confirms that the scaling hypothesis is in place and the value of T_C and critical exponents obtained through several prescriptions are unambiguous and self-consistent.

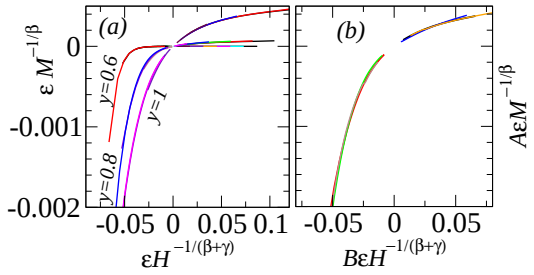

FIG. 2: (a) Scaling collapse of $M - H$ curves for $y = 0.6, 0.8$ and 1 following Eq. (3). Although they appear different, the scaling functions for $y = 0.5, 0.6, 0.8, 1$ can be collapsed onto each other (shown in (b)) by rescaling of axis.

THE SCALING HYPOTHESIS

In the following, we propose a new scaling ansatz which explains the experimental findings presented here. Since diverging fluctuations are known to be the origin of power-laws [55, 56], we start with a scaling relation that relates the exponents of energy and magnetic fluctuations (i.e., α and γ) with that of diverging correlation length associated with criticality:

$$2 - \alpha = d\nu = \gamma \frac{\delta + 1}{\delta - 1}, \tag{4}$$

where ν, α are exponents associated with the correlation length $\xi \sim \varepsilon^{-\nu}$ and specific heat $C_v \sim \varepsilon^{-\alpha}$, d is the dimension. The first equality here relates the diverging correlation length to the energy fluctuation whereas the second equality relates the same to the magnetic fluctuation ($\chi_{AC} \sim \varepsilon^{-\gamma}$ and $\chi_{DC} \sim H^{1/\delta-1}$). If a set of exponents originates from *one* underlying universality class then they must relate to the exponents of the parent universality $\{\alpha_0, \nu_0, \gamma_0, \delta_0\}$ as

$$\nu = \frac{\nu_0}{\lambda^{\kappa+\omega}}; 2 - \alpha = \frac{2 - \alpha_0}{\lambda^{\kappa+\omega}}; \gamma = \frac{\gamma_0}{\lambda^{\omega}}; \frac{\delta + 1}{\delta - 1} = \frac{1}{\lambda^{\kappa}} \frac{\delta_0 + 1}{\delta_0 - 1}, \tag{5}$$

so that the universal scaling relation Eq. (4) remains valid. Here, λ is the marginal parameter that drives the continuous variation and ω and κ are parameters yet to be determined. In Eq. (5), variation of δ, γ are considered independent - equivalently one may vary η, ν independently and deduce variation of other exponents from scaling relations [54].

Clearly $\kappa = 0 = \omega$ is the parent universality class having unscaled ($\lambda = 1$) exponents. Other special cases are when κ or ω vanishes -then corresponding exponent δ or γ remains fixed. When $\kappa = 0$, the continuous variation is governed by $c = \lambda^{\omega}$. In this case we may set $\omega = 1$ without loss of generality and identify $c \equiv \lambda$ as the physical parameter that drives a continuous variation

$$\nu = \frac{\nu_0}{\lambda}; \gamma = \frac{\gamma_0}{\lambda}; 2 - \alpha = \frac{2 - \alpha_0}{\lambda}; \beta = \frac{2 - \alpha - \gamma}{2} = \frac{\beta_0}{\lambda}. \tag{6}$$

This scenario is already known as weak universality where $\delta = 1 + \frac{\gamma}{\beta} = \delta_0$ and $\eta = 2 - \frac{\gamma}{\nu} = \eta_0$ are universal as in the old universality argument [14]. Another special case is $\omega = 0$ and κ set to unity, where γ remains invariant and

$$\nu = \frac{\nu_0}{\lambda}; \delta = \frac{(1+\lambda)\delta_0 + (1-\lambda)}{(1+\lambda) + (1-\lambda)\delta_0}; 2 - \alpha = \frac{2-\alpha_0}{\lambda}. \quad (7)$$

This variation, with λ being the gauge coupling constant, has been observed in strong coupling QED [30]. Now we turn our attention to the generic case $\kappa > 0$ and set $\omega = 1$ (generality is not compromised); the consequent variation of critical exponents is given by

$$\begin{aligned} \nu &= \frac{\nu_0}{\lambda^{\kappa+1}} \; ; \; \gamma = \frac{\gamma_0}{\lambda} \; ; \; \delta = \frac{(1+\lambda^\kappa)\delta_0 + (1-\lambda^\kappa)}{(1+\lambda^\kappa) + (1-\lambda^\kappa)\delta_0}; \\ \beta &= \frac{\beta_0\delta_0\gamma_0}{\lambda\beta_0(\delta-\delta_0) + \lambda\delta\gamma_0} \; ; \; 2 - \eta = \lambda^\kappa(2-\eta_0) \; ; \\ & \quad 2 - \alpha = \lambda^{-(\kappa+1)}(2-\alpha_0). \end{aligned} \quad (8)$$

Note, that this generic variation of exponents satisfies Widom scaling relation $\delta = 1 + \gamma/\beta$ for any λ as long as parent universality class obeys the same.

We further include a possibility that this generic variation may lead to $\beta \to 0$, a special limit where the phase transition becomes discontinuous. At this multicritical limit the usual scaling theory demands $\gamma \to 1$ and $\delta^{-1} \to 0$ [57]. The first requirement can be met if the multicritical point occurs at $\lambda = \gamma_0$ and the second requirement determines

$$\kappa = \frac{1}{\ln \gamma_0} \ln \frac{\delta_0 + 1}{\delta_0 - 1}. \quad (9)$$

In the following, we show that FM transition in $(Sm_{1-y}Nd_y)_{0.52}Sr_{0.48}MnO_3$ exhibits this new universality scenario. For the present experimental system, the parent class is HM3d (at $y = 1$) and accordingly $\kappa = 1.29$ (from Eq. (9) and Table I). At doping $y = 1$, we may set $\lambda = 1$, but a general correspondence between y and and the marginal parameter λ will not be known unless we know the correct interaction Hamiltonian. The best choice of λ that matches the exponents for $y = (0.5, 0.6, 0.8, 1)$ well turns out to be $(1.165, 1.087, 1.03, 1.001)$. The best fit to this data as $y = A(\lambda - \lambda^*)^a$ results in $A = 0.26, \lambda^* = 0.97$ and $a = -0.4$, which is shown in Fig. 3 (b). This is used further in Eq. (8) to get continuous variation of β, γ and $1/\delta$ with respect to y (shown as solid line in Fig. 3 (c)). A good match here supports the the new scaling hypothesis strongly. Moreover Eq. (8) suggests that the transition becomes discontinuous if $\lambda > \gamma_0 = 1.386$ which corresponds to $y \leq 0.37$. In fact, a very sharp growth in the ordered moment along with thermal hysteresis just below T_C has been observed in present system for $y \leq 0.4$ [41], which is also shown in Fig. 3(a). In a related system $(Sm_{1-y}Nd_y)_{0.55}Sr_{0.45}MnO_3$, where Sr concentration

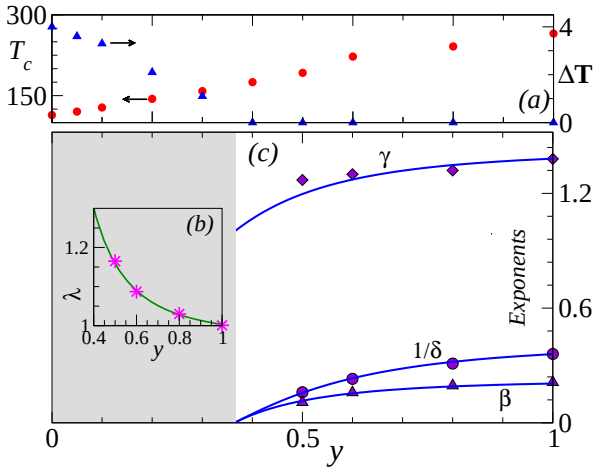

FIG. 3: (a) Critical temperature T_C for heating cycle (red circle) and the thermal hysteresis width ΔT (blue triangle) for different Nd concentration y. The values for $y < 0.5$ are taken from Ref. [41]. (b) The proposed scaling hypothesis has one free parameter λ that maps to y -the best choice gives $y(\lambda) = 0.26/(\lambda - 0.97)^{0.4}$ (solid line). (c) Critical exponents for different y from experiments (symbol) are compared with Eq. (8) (solid lines). Since $\beta \simeq 0$ at $y \simeq 0.37$, one expects a discontinuous transition $y < 0.37$ (also observed in (a)).

differs slightly, the transition remained first order upto $y = 0.33$ [40].

To emphasize that the new scaling hypothesis is indeed in work, we further investigate the scaling functions. If the critical behaviour for different y are related to HM3d, one expects that the seemingly different universal scaling functions $\mathcal{F}$ in Fig. 2 (a) must collapse onto each other if x- and y-axis are scaled by suitable constants. This is described in Fig. 2 (b) - a good collapse of scaling functions for $y = 0.5, 0.6, 0.8, 1$ to a unique universal form further supports that the observed criticality is only a rescaled form of Heisenberg fixed point.

CONCLUSIONS

In conclusion, we have made a comprehensive study of critical phenomena in single crystals of $(Sm_{1-y}Nd_y)_{0.52}Sr_{0.48}MnO_3$ with $0.5 \leq y \leq 1$. The values of critical exponents (β, γ, δ) measured for $y = 1$ are consistent with Heisenberg universality class in three dimension, whereas the same for $y = 0.5, 0.6, 0.8$ are far from any known universality class. All these exponents vary continuously with y, but they seem to obey the standard scaling laws following a single equation of state. Variation of exponents is not new to critical phenomena as it can be generated by a marginal interaction, but most examples (though there are a few exceptions) in both theoretical and experimental studies satisfy the weak universality [14] where $\{\beta, \gamma, \nu\}$ vary but $\{\eta, \delta\}$ are fixed. We

argue that, to be consistent with scaling, the continuous variation must occur in specific ways. Two special cases are, (a) δ remains unchanged, which leads to the weak universality, and (b) γ is unaltered, which results in a kind of variation observed in strong coupling QED [30]. This generic universality scenario, which leads to a multicritical point, explains the continuous variation of critical exponents observed in $(Sm_{1-y}Nd_y)_{0.52}Sr_{0.48}MnO_3$ and correctly predicts the possibility of a discontinuous transition for doping $y < 0.37$.

A marginal interaction that could provide variation of critical exponents beyond weak universality remains elusive - it is certainly challenging to device a microscopic theory to accommodate this phenomenon. Here, disorder certainly plays a role in generating anomalous magnetic fluctuations. In addition, quantum fluctuations, if present, may bring in additional features to the proposed scaling hypothesis; such a possibility has been conjectured in recent experiments [34], but a rigorous and convincing microscopic theory is still lacking. In particular, it is not clear, how or why a marginal operator is generated in all the above experimental conditions to drive continuous variations in specific ways.

Acknowledgements : The authors would like to thank Mr. A. Pal for technical assistance.

* Electronic address: pk.mohanty@saha.ac.in

[1] Griffiths, R. B. Dependence of critical indices on a parameter. *Phys. Rev. Lett.* **24**, 1479-1482 (1970).

[2] Stanley, H. E. Scaling, universality, and renormalization: three pillars of modern critical phenomena. *Rev. Mod. Phys.* **71**, S358-S366 (1999).

[3] Kadanoff, L. P. Statistical physics: statics, dynamics and renormalization (World Scientific Publishing, 2000).

[4] Wilson, K. G. & Kogut, J. The renormalization group and the ϵ expansion. *Physics Reports* **12**, 75-199 (1974).

[5] Guggenheim, E. A. The principle of corresponding states. *Chem. Phys.* **13**, 253-261 (1945).

[6] Back, C. H. *et al.* Experimental confermation of universality for a phase transition in two dimensions. *Nature* **378**, 597-600 (2005).

[7] Baxter, R. J. Eight-vertex model in lattice statistics. *Phys. Rev. Lett.* **26**, 832-833 (1971).

[8] Sutherland, B. Two-dimensional hydrogen bonded crystals without the ice rule. *J. Math. Phys.* **11**, 3183-3186 (1970).

[9] Kadanoff, L. P. & Wagner, F. J. Some critical properties of the eight-vertex model. *Phys. Rev. B* **4**, 3989-3993 (1971).

[10] Fan, C. & Wu, F. Y. General lattice model of phase transitions. *Phys. Rev. B* **2**, 723-733 (1970).

[11] Ashkin, J. & Teller, E. Statistics of two-dimensional lattices with four components. *Phys. Rev.* **64**, 178-184 (1943).

[12] Kadanoff, L. P. Connections between the Critical behavior of the planar model and that of the eight-vertex model. *Phys. Rev. Lett.* **39**, 903-905 (1977).

[13] Zisook, A. B. Second-order expansion of indices in the generalised Villain model. *J. Phys. A: Math. Gen.* **13**, 2451-2455 (1980).

[14] Suzuki, M. New universality of critical exponents. *Prog. Theor. Phys.* **51**, 1992-1993 (1974).

[15] Queiroz, S. L. A. de. Scaling behavior of a square-lattice Ising model with competing interactions in a uniform field. *Phys. Rev. E* **84**, 031132 (2011).

[16] Jin, S., Sen, A. & Sandvik, A. W. Ashkin-Teller criticality and pseudo-first-order behavior in a frustrated Ising model on the square lattice. *Phys. Rev. Lett.* **108**, 045702 (2012).

[17] Alet, F. *et al.* Interacting classical dimers on the square lattice. *Phys. Rev. Lett.* **94**, 235702 (2005).

[18] Pearce, P. A. & Kim, D. Continuously varying exponents in magnetic hard squares. *J. Phys. A: Math. Gen.* **20**, 6471-6485 (1987).

[19] Malakis, A., Berker, A. N., Hadjiagapiou, I. A. & Fytas, N. G. Strong violation of critical phenomena universality: Wang-Landau study of the two-dimensional Blume-Capel model under bond randomness. *Phys. Rev. E* **79**, 011125 (2009).

[20] Newman, T. J. Continuously varying exponents in reaction-diffusion systems. *J. Phys. A: Math. Gen.* **28**, L183-L190 (1995).

[21] Noh. J. D. & Park, H. Universality class of absorbing transitions with continuously varying critical exponents. *Phys. Rev. E* **69**, 016122 (2004).

[22] Andrade, R. F. S. & Herrmann, H. J. Percolation model with continuously varying exponents. *Phys. Rev. E* **88**, 042122 (2013).

[23] Sahara, R., Mizuseki, H., Ohno, K. & Kawazoe, Y. Site-percolation models including heterogeneous particles on a square lattice. *Mater. Trans. JIM* **40**, 1314-1318 (1999).

[24] Monceau, P. & Hsiao, P. Y. Direct evidence for weak universality on fractal structures. *Physica A* **331**, 1-9 (2004).

[25] Suzuki, T., Harada, K., Matsuo, H., Todo, S. & Kawashima, N. Thermal phase transition of generalized Heisenberg models for SU(N) spins on square and honeycomb lattices. *Phys. Rev. B* **91**, 094414 (2015).

[26] Bernardi, L. & Campbell, I. A. Violation of universality for Ising spin-glass transitions. *Phys. Rev. B* **52**, 12501-12504 (1995).

[27] Corti, M., Degiorgio, V. & Zulauf, M. Nonuniversal critical behavior of micellar solutions. *Phys. Rev. Lett.* **48**, 1617-1620 (1982).

[28] Fisher, M. E. Long-range crossover and "nonuniversal" exponents in micellar solutions. *Phys. Rev. Lett.* **57**, 1911-1914 (1986).

[29] Bekhechi, S. & Southern, B. W. Low-temperature static and dynamic behavior of the easy-axis Heisenberg antiferromagnet on the Kagome lattice. *Phys. Rev. B* **67**, 144403 (2003).

[30] Kondo, K. I. Critical exponents, scaling law, universality and renormalization group flow in strong coupling QED. *Int. J. Mod. Phys. A* **6**, 5447-5466 (1991).

[31] Kida, T. *et al.* Unconventional critical behavior in the weak ferromagnet $BaIrO_3$. *Euro. Phys. Lett.* **84**, 27004 (2008).

[32] Omerzu, A., Tokumoto, M., Tadić, B. & Mihailovic, D. Critical exponents at the ferromagnetic transition in tetrakis(dimethylamino)ethylene - C_{60} (TDAE-C_{60}). *Phys. Rev. Lett.* **87**, 177205 (2001).

[33] Kagawa, F., Miyagawa, K. & Kanoda, k. Unconventional critical behaviour in a quasi-two-dimensional organic conductor. *Nature* **436**, 534-537 (2005).

[34] Fuchs, D. *et al.* Critical scaling analysis of the itinerant ferromagnet $Sr_{1-x}Ca_xRuO_3$. *Phys. Rev. B* **89**, 174405 (2014).

[35] Tokura, Y. Critical features of colossal magnetoresistive manganites. *Rep. Prog. Phys.* **69**, 797-851 (2006).

[36] Mahesh, R. & Itoh, M. Role of size mismatch of $A-$site cations on the first-order transition in manganates. *Phys. Rev. B* **60**, 2994-2997 (1999).

[37] Tomioka, Y., Asamitsu, A., Kuwahara, H., Moritomo, Y. & Tokura, Y. Magnetic-field-induced metal-insulator phenomena in $Pr_{1-x}Ca_xMnO_3$ with controlled charge-ordering instability. *Phys. Rev. B* **53**, R1689-R1692 (1996).

[38] Kim, D. *et al.* Tricritical point and the doping dependence of the Order of the ferromagnetic phase transition of $La_{1-x}Ca_xMnO_3$. *Phys. Rev. Lett.* **89**, 227202 (2002).

[39] Fisher, L. M. *et al.* Quenched-disorder-induced magnetization jumps in (Sm,Sr)MnO_3. *Phys. Rev. B* **70**, 212411 (2004).

[40] Demkó, L. *et al.* Multicritical end point of the first-order ferromagnetic transition in colossal magnetoresistive manganites. *Phys. Rev. Lett.* **101**, 037206 (2008).

[41] Sarkar, P. *et al.* Role of external and internal perturbations on the ferromagnetic phase transition in $Sm_{0.52}Sr_{0.48}MnO_3$. *Phys. Rev. B* **79**, 144431 (2009).

[42] Sarkar, P. *et al.* Pressure induced critical behavior of ferromagnetic phase transition in Sm-Nd-Sr manganites. *Phys. Rev. Lett.* **103**, 057205 (2009).

[43] Tomioka, Y., Kumai, R., Ito, T. & Tokura, Y. Magnetic and electronic properties of $Eu_{1-x}Sr_xMnO_3$ ($0.3< x <0.7$) single crystals. *Phys. Rev. B* **80**, 174414 (2009).

[44] Salamon, M. B. & Chun, S. H. Griffiths singularities and magnetoresistive manganites. *Phys. Rev. B* **68**, 014411 (2003).

[45] Jiang, W., Zhou, X., Williams, G., Mukovskii, Y. & Privezentsev, R. The evolution of Griffiths-phase-like features and colossal magnetoresistance in $La_{1-x}Ca_xMnO_3$ ($0.18 \leq x \leq 0.27$) across the compositional metal−insulator boundary. *J. Phys.: Cond. Mat.* **21**, 415603 (2009).

[46] Phan, T. L., Zhang, Y. D., Zhang, P., Thanh, T. D. & Yu, S. C. Critical behavior and magnetic-entropy change of orthorhombic $La_{0.7}Ca_{0.2}Sr_{0.1}MnO_3$. *J. Appl. Phys.* **112**, 093906 (2012).

[47] Dagotto, E., Hotta, T. & Moreo, A. Collosal magnetoresistant materials: the key role of phase separation. *Phys. Rep.* **344**, 1 (2001).

[48] Rodriguez-Martinez, L. M. & Attfield, J. P. Cation disorder and size effects in magnetoresistive manganese oxide perovskites. *Phys. Rev. B* **54**, R15622 (1996).

[49] Sato, T. J., Lin, J. W. & Dabrowski, B. Disorder-induced polaron formation in the magnetoresistive perovskite $La_{0.54}Ba_{0.46}MnO_3$. *Phys. Rev. Lett.* **93**, 267204 (2004).

[50] Babushkina, N. A. *et al.* Modification of the ground state in Sm-Sr manganites by oxygen isotope substitution. *Phys. Rev. B* **67**, 100410(R) (2003).

[51] Stanley, H. E. Introduction to Phase Transitions and Critical Phenomena (Oxford University Press, 1971).

[52] Arrott, A. & Noakes, J. E. Approximate equation of state for nickel near its critical temperature. *Phys. Rev. Lett.* **19**, 786-789 (1967).

[53] Kouvel, J. S. & Fisher, M. E. Detailed Magnetic Behavior of Nickel Near its Curie Point. *Phys. Rev.* **136**, A1626-A1632 (1964).

[54] See supplementary information for details.

[55] Das, A., Chatterjee, S., Pradhan, P. & Mohanty, P. K. Additivity property and emergence of power laws in nonequilibrium steady states. *Phys. Rev. E* **92** , 052107 (2015).

[56] A detailed proof for non-equilibrium systems is given in [55], which also holds trivially for equilibrium.

[57] Fisher, M. E. & Berker, A. N. Scaling for first-order phase transitions in thermodynamic and finite systems. *Phys. Rev. B* **26**, 2507-2513 (1982).

[58] Mandal, P., Bandyopadhyay, B. & Ghosh, B. Resistivity anomaly in the vicinity of a structural phase transition in $La_{1-x}Sr_xMnO_3$. *Phys. Rev. B* **64**, 180405(R) (2001).

[59] Mandal, P. & Ghosh, B. Transport, magnetic, and structural properties of $La_{1-x}M_xMnO_3$ (M = Ba, Sr, Ca) for $0 \leq x \leq 0.20$. *Phys. Rev. B* **68**, 014422 (2003).